

Journal of Materials Chemistry A

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: Z. Li, G. M. Treich, M. Tefferi, C. Wu, S. Nasreen, S. K. Scheirey, R. Ramprasad, G. A. Sotzing and Y. Cao, *J. Mater. Chem. A*, 2019, DOI: 10.1039/C9TA03601F.




This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [author guidelines](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the ethical guidelines, outlined in our [author and reviewer resource centre](#), still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Table of content

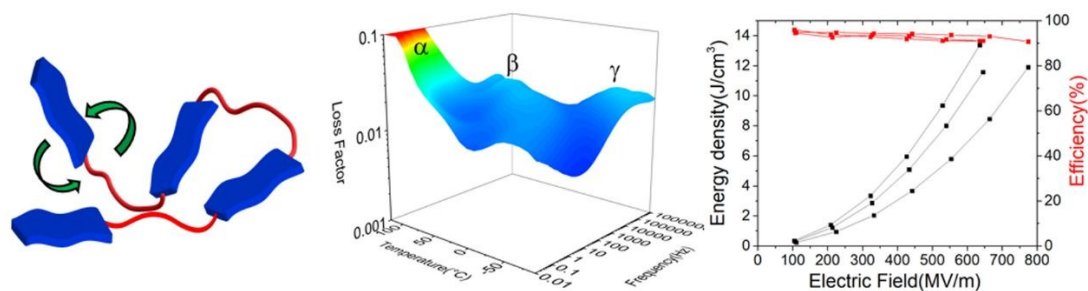

Dielectric constant of polymers was increased by combining flexible segments and rigid polar segments in the polymer backbone.

COMMUNICATION

High Energy Density and High Efficiency All-Organic Polymers with Enhanced Dipolar Polarization

Zongze Li^{a,b}, Gregory M. Treich^c, Matthew Tefferi^{a,b}, Chao Wu^b, Shamima Nasreen^c, Sydney K. Scheirey^c, Rampi Ramprasad^d, Gregory A. Sotzing^c, and Yang Cao^{a,b*}Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Advanced polymers with high energy density and high efficiency are urgently needed in pulse power capacitor applications. Here, we present a practical design approach towards all-organic polymers with high energy density and high efficiency by enhancing dipolar polarization from the molecular level. Flexible segments were introduced into the backbones of rigid polar aromatic polymers to increase the flexibility of dipoles. Dielectric spectroscopy measurement on designed polymers revealed multiple strong sub-glass transition (sub- T_g) relaxation peaks with low activation energies, which indicated the enhanced movement freedom of dipoles below the glass transition temperature. As a result, dielectric constants were increased up to 46% when compared with their base polymers and D-E loop measurement showed that all these designed polymers had high energy densities above 11 J/cm^3 with efficiency above 90%. These results unveiled a novel approach towards high dielectric constant organic polymers for electrical energy storage.

Polymer film capacitors are widely used as electrical energy storage devices for pulse power supply and power conditioning applications.¹⁻⁴ Polymer capacitors have advantages of high voltage scalability, low loss, fast discharging speed and graceful failure mode when compared with ceramic capacitors, supercapacitors or pseudocapacitors.⁵ Biaxially oriented polypropylene (BOPP), predominant in commercial polymer film capacitors, has a high breakdown strength ($>730 \text{ MV/m}$) with very high efficiency ($>94\%$). However, its low dielectric constant ($k=2.2$) results in a limited energy density ($\sim 5 \text{ J/cm}^3$).⁶

Further development in advanced electrical devices to meet future needs calls for new polymers with high energy density as well as high efficiency to replace BOPP.⁷

From the energy density (U) equation $U=0.5\epsilon_0\epsilon_r E^2$ for linear dielectrics, we can see that the energy density can be enhanced by increasing dielectric constant (ϵ_r) or breakdown strength (E). Currently, the highest breakdown strength for all-organic polymers is $\sim 1 \text{ GV/m}$, with limited room for further improvement. Therefore, increasing the dielectric constant appears to be a more practical approach. Intensive research has been carried out towards miniaturized polymer film capacitors with high k polymers.⁸ A straightforward solution was to introduce high dielectric constant inorganic fillers into the polymer matrix by materials engineering. Materials including polymer blends,⁹ nanolaminates,¹⁰ nanocomposites^{11, 12} and nanocoating,¹³ etc have been demonstrated with high dielectric constant. However, until now, no such polymers have been used in capacitors due to fundamental limitations. Inorganic fillers could lead to low efficiency because of mismatching between the filler and polymer matrix. The existence of the interface was a potential threat for long-term reliability and made large-scale film fabrication challenging.¹⁴

Thus, it is highly imperative to synthesize polymers with high dielectric constant and low loss over a broad range of frequency and temperature.¹⁵ There are mainly four types of polarization that can contribute to the dielectric constant: electronic, ionic, dipolar (orientational), and interfacial polarization.¹⁶ Interfacial polarization is not desired for capacitor applications because it comes with huge dielectric loss.¹⁷ Electronic and ionic polarization occur at very high frequencies ($>10^{11} \text{ Hz}$) with almost no loss penalty and are therefore preferred sources of polarization for energy storage purposes. Rational co-designs of high energy density polymers by utilizing electronic and ionic polarization have identified several polar aromatic and organometallic polymers with high dielectric constant.¹⁸ However, that study also indicated an inverse relationship between the band gap and electronic polarization. In order to maintain a high enough band gap ($>4 \text{ eV}$) to support the


^a Department of Electrical and Computer Engineering, University of Connecticut, 371 Fairfield Way, Storrs, Connecticut 06269, United States.
E-mail: yang.cao@uconn.edu

^b Electrical Insulation Research Center, Institute of Materials Science, University of Connecticut, 97 N Eagleville Rd, Storrs, CT 06269, United States

^c Polymer Program, Institute of Materials Science, University of Connecticut, 97 N Eagleville Rd, Storrs, CT 06269, United States

^d School of Materials Science and Engineering, Georgia Institute of Technology, 771 Ferst Drive, Atlanta, GA 30332, United States

Electronic Supplementary Information (ESI) available: See DOI: 10.1039/x0xx00000x

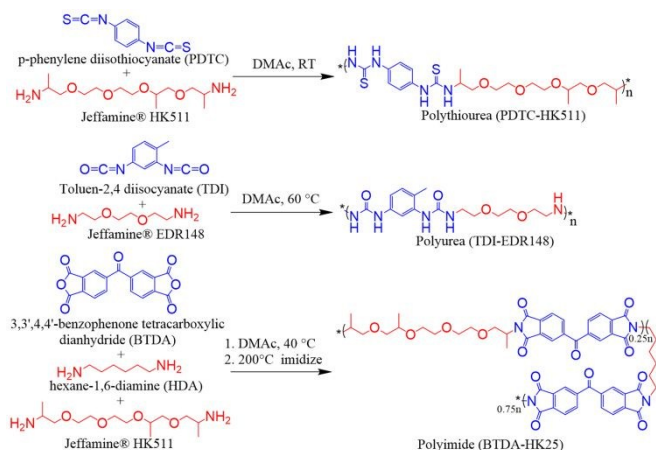

Scheme 1. Polymerization reaction scheme of three designed polymers: PDC-HK511, TDI-EDR148 and BTDA-HK25.

breakdown strength (and hence limited electronic polarization), new all-organic polymers with further enhanced ionic and/or dipolar polarization appear to be the most promising way to increase the dielectric constant beyond 4.¹⁹

Dipolar polarization, also known as orientational polarization, is an important mechanism that occurs at the frequency range of $\sim 10^8$ Hz with a low dielectric loss. Increasing dipolar polarization can be achieved by utilizing relaxor ferroelectric based copolymers,²⁰ by introducing polar side groups into glassy polymers,^{21,22} or by modifying polymers known for high dielectric constant.²³ It is noteworthy that increasing dipolar polarization in organic polymers often leads to dramatic decreases in discharge efficiency due to multiple loss mechanisms. For example, ferroelectrics suffer from low efficiency because of intrinsic hysteresis loss. By and large, the aforementioned approaches encountered high loss due to

strong convoluted coupling between the dipolar orientations and global chain motions. Polymers with a discharge efficiency lower than 90% are generally not practical for capacitor applications because of potential thermal breakdown, regardless of high energy density or high dielectric constant. The main challenge here is to increase dipolar polarization while maintaining the low dielectric loss and other properties.

In this paper, we present a novel yet practical approach to design promising pure organic high k , low loss polymers by introducing flexible segments into backbones of polar aromatic polymers. Specifically, we showed that by introducing flexible ether-linkage segments into backbones of aromatic polyurea, polythiourea and polyimide, energy densities in these polymers were significantly improved as a result of enhanced dipolar polarization. The enhancement of dipolar polarization was realized via “secondary” processes c.a. pendant side groups or crank-shafting chain segments undergoing local, uncorrelated re-orientations.^{24, 25} Furthermore, the aromatic rigid segments ensured sufficiently high glass transitions that decoupled these local re-orientations from primary chain relaxation. These rigid segments also “carved” out free volume to allow increased local re-orientational freedom of dipoles with reduced dipole constraints and thus supported a high discharge efficiency. Three designed polymers were synthesized by addition reactions and free-standing films were produced. A systematic comparative characterization of these novel polymers was given to study their polarization behavior and energy storage capability. Dielectric constants of 4.5-6.6 and loss factors below 0.02 were found on these polymers at room temperature. The dielectric constant showed an increase of >1.5 compared to that of the base polar aromatic polymers. Broadband dielectric spectroscopy revealed strong sub- T_g relaxation peaks, which were related to multiple polarization processes of polar segments. The low activation energy for each relaxation process


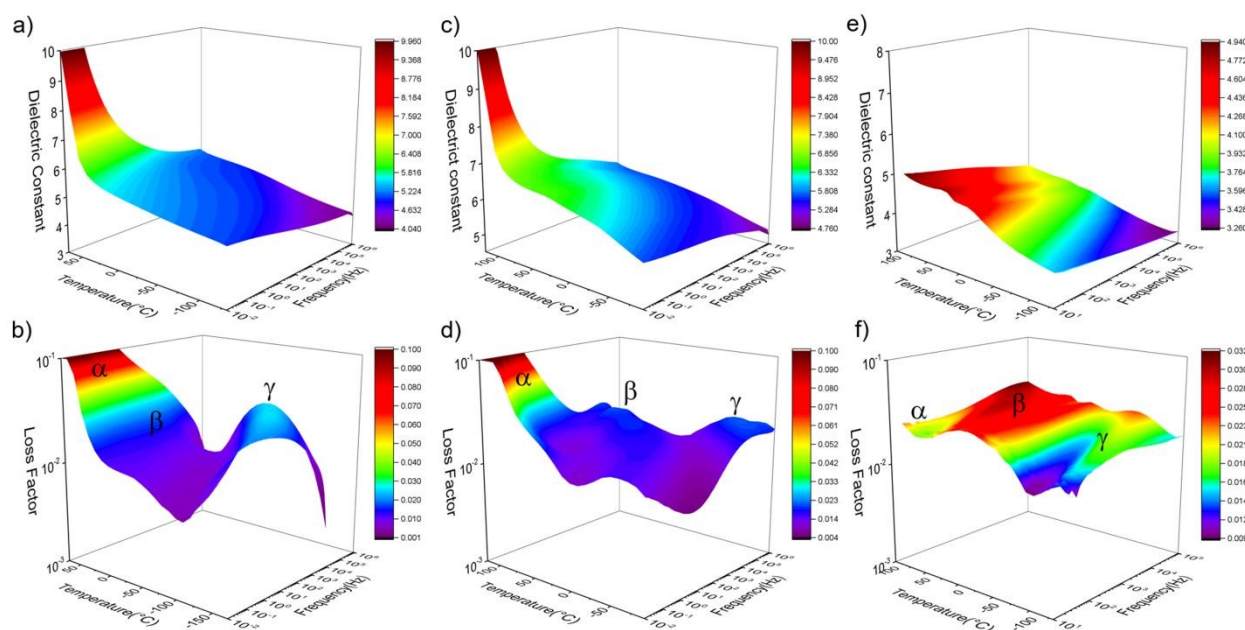


Figure 1. The Broadband dielectric spectroscopy as a function of wide ranges of temperatures and frequencies. Measurement results of dielectric constant for a) PDC-HK511, c) TDI-EDR148, e) BTDA-HK25, and loss factor for b) PDC-HK511, d) TDI-EDR148 and f) BTDA-HK25.

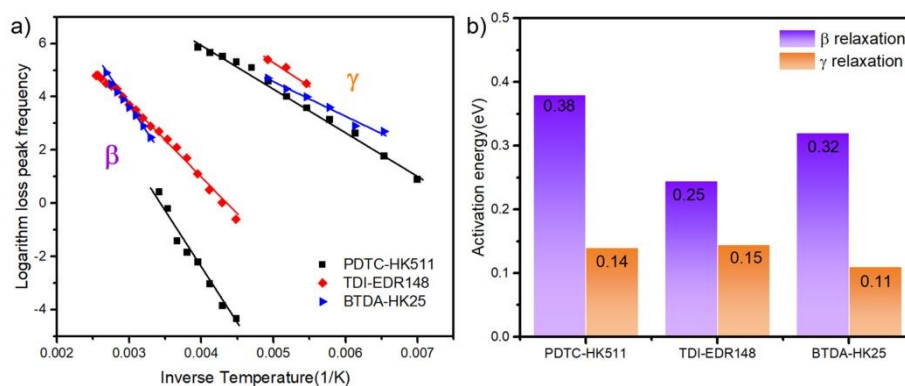

View Article Online
DOI: 10.1039/C9TA03601F

Figure 2. a) The temperature dependence of loss peak maximum according to Arrhenius equation. b) Calculated activation energies for each sub- T_g relaxation process based on Arrhenius equation.

confirmed the ease of movement for dipoles. D-E loops measurement showed that these polymers achieved high energy density (>11 J/cm³) with efficiency higher than 90%. These values are outstanding among organic thin film polymers for capacitor applications. The results and findings presented here pave the way to further increase the energy density of all-organic polymers and explore new candidates for advanced capacitors.

Scheme 1 shows general reaction procedures for the synthesis of the three designed polymers. The first polymer in the polythiourea family named PDTC-HK511 was prepared through addition reactions of para-phenylene diisothiocyanate (PDTC) and Jeffamine HK511. The second polymer in the polyurea family named TDI-EDR148 was prepared through addition reactions of toluene-2, 4-diisocyanate (TDI) and Jeffamine EDR148. The third polymer from the polyimide family named BTDA-HK25 was prepared through addition reactions of 3,3',4,4'-benzophenone tetracarboxylic dianhydride (BTDA), Jeffamine HK511 and hexane-1,6-diamine (HDA). It was a copolymer of BTDA-HK511 and BTDA-HDA, where the molar ratio of BTDA-HK511 is 25%. BTDA-HK25 was chosen for its balanced dielectric and thermal properties (see supporting information). Thin films were made with filtered polymer solution on a glass substrate using a film coater. As shown in Figure S1, the obtained polymer films were free-standing, 10–15 μ m thick, and transparent. All polymers were characterized by ¹H NMR and FTIR to confirm the products of reactions (Figure S2). Thermal properties were also fully characterized (Figure S3 & S4) and the results were summarized in Table S1.

The real and imaginary parts of the complex dielectric permittivity from broadband dielectric spectroscopy were shown in Figure 1. At room temperature, all three polymers showed high dielectric constants above 4.5 and low dielectric loss factors below 0.02 at 1 kHz. PDTC-HK511 was shown to have a dielectric constant of around 5.8 with a loss factor of 0.012. TDI-EDR148 showed the highest dielectric constant of 6.6 and a loss factor of 0.018. BTDA-HK25 showed the lowest loss

Table 1. The breakdown of dielectric constant into separate polarization processes.

	$\epsilon_{\text{electronic}}$	ϵ_{atomic}	$\epsilon_{\text{dipolar}}$	ϵ_{total}	Dipolar enhancement ^[a]
PDTC-HK511	2.69	1.35	1.76	5.80	43.6%
TDI-EDR148	2.58	2.18	1.84	6.60	38.7%
BTDA-HK25	2.69	0.57	1.51	4.77	46.3%

[a] $\epsilon_{\text{dipolar}}$ compared with $\epsilon_{\text{electronic}} + \epsilon_{\text{atomic}}$

factor of less than 0.01 and a dielectric constant of 4.5 (Figure S5).

Strong sub- T_g relaxation loss peaks were observed from Figure 1b, d and f. The relaxation peak under high temperature relating to the glass transition is α relaxation. The following relaxation peak is β relaxation which related to crankshaft movements in polymer chains.²⁶ The γ relaxation peak under low temperature and high frequency is a result of local fluctuations of dipole vectors within a polymer chain. These observed β and γ relaxation peaks indicated strong localized dipole movement as a function of applied field. The observed sub- T_g relaxation, especially the γ process, showed a high characteristic frequency according to the loss peak. This fast response polarization process came with very small loss penalty for capacitors.

From Figure 1a, c and e, we can see that the dielectric constant increased following each relaxation process according to the Kramer-Kronig relation.²⁷ The dielectric constant measured under -130°C in each polymer was roughly the same as the machine learning predicted value on each base aromatic polymer without adding the flexible segments.²⁸ At such low temperature, dipolar polarization was “frozen” because of solid-state energy barrier and the measured dielectric constant was all from electronic and atomic polarization. The contribution of each polarization process was given in Table 1 based on the refractive index measurement (see Supporting information page S7). Dipolar polarization processes helped these designed polymers to enhance their dielectric constants more than 38% with increases larger than 1.5. Thus, the resulting dielectric constant of these designed polymers was higher than most polymers within their own class.²⁹⁻³¹

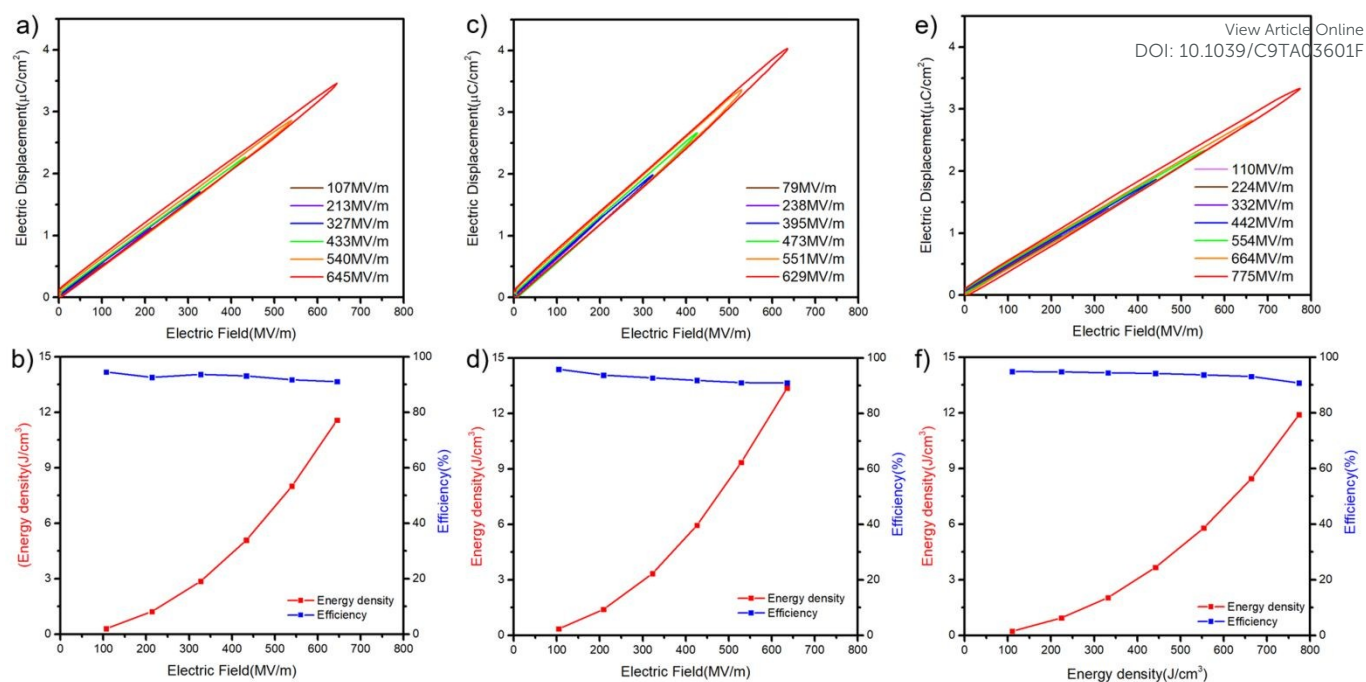


Figure 3. High electric field D-E loop results. a) D-E loops for PDTC-HK511 and b) corresponding total energy density and efficiency. c) D-E loops for TDI-EDR148 and d) corresponding total energy density and efficiency. e) D-E loops for BTDA-HK25 and f) corresponding total energy density and efficiency.

To shine more light on the correlation between the designed polymer structure and the dielectric polarization behavior, activation energy of each relaxation process was extracted by using the Havriliak and Negami (HN) model as an indicator of the dipole rotation energy barrier.^{32,33} According to the model, peak frequency at each temperature point will follow the Arrhenius-type temperature dependence. The scaling behavior predicted by the Arrhenius equation with $\log(f)$ vs. $1/T$ will yield a straight line with a slope that is proportional to the activation energy. Figure 2a showed the peak frequency vs the reverse temperature plots according to the Arrhenius equation for all three polymers based on the dielectric spectroscopy measurement. Each data point corresponded to a relaxation peak frequency and fell into separate regions for β and γ relaxation. Each relaxation process followed a unique straight line, indicating Arrhenius type of distribution. Linear curve fitting was performed, and the resulting activation energies of all sub- T_g relaxation processes were summarized in Figure 2b. The activation energies for β relaxation were 0.38 eV, 0.25 eV and 0.32 eV for PDTC-HK511, TDI-EDR148 and BTDA-HK25, respectively. The activation energies for γ relaxation were 0.14 eV, 0.15 eV and 0.11 eV, respectively. Activation energies for both β and γ relaxation processes were similar in these polymers, indicating similar polarization behaviors. These activation energies were considered to be relatively low when compared with polypropylene, which had a value of 1.21 eV for β relaxation^[16] and a value of 0.48 eV for γ relaxation.³⁴

The low activation energy of each relaxation process indicated the movement freedom of those dipoles under the external field. Those starting aromatic polar polymers had relatively high dielectric constants stemming from electronic

and ionic polarization, however, their rigid structures with limited movement freedom lead to weak dipolar polarization as dipoles could not rotate freely. The flexible segments added to the backbone gave the polymer chain extra flexibility for the local segments movement. These polar groups with orientation freedom were polarized following the external field and contributed to the overall dielectric constant. With the combination of rigid and flexible segments, free volume was created in the polymer and constraints on dipoles were reduced. Thus, this rotational freedom also contributed to the low dielectric loss factor.

The electrical energy storage capability of these polymers was studied under high field with unipolar D-E loop measurements and the results are summarized in Figure 3. High dielectric constants, high energy densities and high efficiencies were observed on all designed polymers. The apparent dielectric constant could be estimated from the slope of the charging loops and the value of 5.5 for PDTC-HK511, 6.4 for TDI-EDR148 and 4.5 for BTDA-HK25 agreed well with the dielectric measurement results in Figure 1. All three polymers showed narrow D-E loops, and breakdown strengths up to 780 MV/m was achieved. These high breakdown strengths came from the selected rigid aromatic segments with large band gap and the high dielectric constant could be attributed to the enhanced dipolar polarization.

The energy density and efficiency were calculated from the D-E loop results. The energy density obviously increased with the applied electric field and the efficiency decreased with the applied field as a result of conduction and other loss mechanisms. The maximum energy densities were 11 J/cm^3 , 13 J/cm^3 , and 12 J/cm^3 for PDTC-HK511, TDI-EDR148, and BTDA-

HK25, respectively, all with efficiencies above 90% at breakdown field. All polymers showed at least doubled energy densities when compared to BOPP, with relatively high efficiencies. These values are outstanding among organic thin film polymers for capacitor applications.

Conclusions

In conclusion, we have introduced a novel molecular engineering design approach for high energy density and high efficiency polymers. Dipolar polarization was enhanced by combining rigid aromatic polymers with flexible segments in the polymer backbones. The aromatic segments provided a high band gap and high glass transition temperature, and the flexible segments gave dipoles the flexibility to rotate and created more free volume. Three polymers were synthesized based on this design methodology and free-standing films with large size were produced. These polymer films have enhanced dielectric constants (up to 45%) compared with their base polymers, with high energy densities of up to 13 J/cm³ and high efficiency above 90%. Broadband dielectric spectroscopy showed multiple strong sub-T_g polarization processes with low activation energies compared with BOPP. These results confirmed the orientational flexibility of dipoles and the enhancement of dipolar polarization originating from the designed structure. With the designed molecular structure, the energy density and efficiency of these polymers were remarkably higher than other polymers within their own classes. These findings pave a way to further increase the energy density of organic polymers and explore novel high energy density polymers.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work is supported through a multidisciplinary university research initiative (MURI) grant (N00014-10-1-0944) and a Rational Design of Polymer Dielectrics grant (N00014-16-1-2580), both through the Office of Naval Research. The authors would like to thank JoAnne Ronzello for the help on dielectric measurements.

References

- Q. Tan, P. Irwin and Y. Cao, *IEEE Trans. Fund. Mater.*, 2006, **126**, 1153-1159.
- W. Sarjeant, I. W. Clelland and R. A. Price, *Proc. IEEE*, 2001, **89**, 846-855.
- Q. Li, L. Chen, M. R. Gadinski, S. Zhang, G. Zhang, H. U. Li, E. Iagodkine, A. Haque, L.-Q. Chen and T. N. Jackson, *Nature*, 2015, **523**, 576-579.
- Z. Yao, Z. Song, H. Hao, Z. Yu, M. Cao, S. Zhang, M. T. Lanagan and H. Liu, *Adv. Mater.*, 2017, **29**, 1601727.
- W. J. Sarjeant, J. Zirnheld, F. W. MacDougall, J. Bowers, N. Clark, I. Clelland, R. Price, M. Hudis, I. Kohlberg and G. McDuff, in *Handbook of Low and High Dielectric Constant Materials and Their Applications*, Elsevier, 1999, pp. 423-491.
- J. L. Nash, *Polym. Eng. Sci.*, 1988, **28**, 862-870.
- US DOE Basic Energy Sciences Workshop Report, *Basic Research Needs for Materials under Extreme Environments*, 2008.
- Q. Chen, Y. Shen, S. Zhang and Q. Zhang, *Annu. Rev. Mater. Res.*, 2015, **45**, 433-458.
- Y. Thakur, B. Zhang, R. Dong, W. Lu, C. Jacob, J. Runt, J. Bernholc and Q. Zhang, *Nano Energy*, 2017, **32**, 73-79.
- M. Mackey, D. E. Schuele, L. Zhu, L. Flandin, M. A. Wolak, J. S. Shirk, A. Hiltner and E. Baer, *Macromolecules*, 2012, **45**, 1954-1962.
- X. Huang and P. Jiang, *Adv. Mater.*, 2015, **27**, 546-554.
- K. Yang, X. Huang, J. He and P. Jiang, *Adv. Mater. Interfaces*, 2015, **2**, 1500361.
- B. Zhang, Z. Li, M. Ren, J. Liu, T. Moran, B. Huey, L. Sun, Y. Cao, in *2017 IEEE Conference on Electrical Insulation and Dielectric Phenomenon (CEIDP)*, 2017, pp. 461-464.
- K. C. Kao, *Dielectric phenomena in solids*, Elsevier, 2004.
- G. M. Treich, M. Tefferi, S. Nasreen, A. Mannodi-Kanakkithodi, Z. Li, R. Ramprasad, G. A. Sotzing and Y. Cao, *IEEE Trans. Dielectr. Electr. Insul.*, 2017, **24**, 732-743.
- G. G. Raju, *Dielectrics in electric fields*, CRC press, 2016.
- S. H. Kim, K. Hong, W. Xie, K. H. Lee, S. Zhang, T. P. Lodge, C. D. J. A. M. Frisbie, *Adv. Mater.*, 2013, **25**, 1822-1846.
- A. Mannodi-Kanakkithodi, G. M. Treich, T. D. Huan, R. Ma, M. Tefferi, Y. Cao, G. A. Sotzing, R. Ramprasad, *Adv. Mater.* 2016, **28**, 6277-6291.
- E. Baer, L. Zhu, *Macromolecules* 2017, **50**, 2239-2256.
- B. Chu, X. Zhou, K. Ren, B. Neese, M. Lin, Q. Wang, F. Bauer, Q. Zhang, *Science*, 2006, **313**, 334-336.
- Z. Zhang, D. H. Wang, M. H. Litt, L. S. Tan, L. Zhu, *Angew. Chem.*, 2018, **130**, 1544-1547.
- D. H. Wang, B. A. Kurish, I. Treufeld, L. Zhu, L. S. Tan, *J. Polym. Sci., Part A: Polym. Chem.*, 2015, **53**, 422-436.
- Y. Thakur, M. Lin, S. Wu, Z. Cheng, D.-Y. Jeong and Q. Zhang, *J. Appl. Phys.*, 2015, **117**, 114104.
- R. Casalini and C. Roland, *J. Chem. Phys.*, 2009, **131**, 114501.
- T. Hecksher, A. I. Nielsen, N. B. Olsen and J. C. Dyre, *Nat. Phys.*, 2008, **4**, 737-741.
- N. G. McCrum, B. E. Read and G. Williams, *Anelastic and Dielectric Effects in Polymeric Solids*, Wiley, 1967.
- F. Kremer and A. Schönhal, in *Broadband Dielectric Spectroscopy*, Springer, 2002, pp. 99-129.
- C. Kim, A. Chandrasekaran, T. D. Huan, D. Das and R. Ramprasad, *J. Phys. Chem. C*, 2018, **122**, 17575-17585.
- Q. Burlingame, S. Wu, M. Lin and Q. Zhang, *Adv. Energy Mater.*, 2013, **3**, 1051-1055.
- S. Wu, Q. Burlingame, Z.-X. Cheng, M. Lin and Q. Zhang, *J. Electron. Mater.*, 2014, **43**, 4548-4551.
- R. Ma, A. F. Baldwin, C. Wang, I. Offenbach, M. Cakmak, R. Ramprasad and G. A. Sotzing, *ACS Appl. Mater. Interfaces*, 2014, **6**, 10445-10451.
- S. Havriliak and S. Negami, *Polymer*, 1967, **8**, 161-210.
- S. Havriliak and S. Negami, *J. Polym. Sci., Part C: Polym. Symp.*, 1966, **14**, 99-117.
- P. Frübing, D. Blischke, R. Gerhard-Multhaupt and M. S. Khalil, *J. Phys. D: Appl. Phys.*, 2001, **34**, 3051-3057.