

## Chemically Recyclable Polymer System Based on Nucleophilic Aromatic Ring-Opening Polymerization

Yong-Liang Su, Liang Yue, Huan Tran, Mizhi Xu, Anthony Engler, Rampi Ramprasad, H. Jerry Qi, and Will R. Gutekunst\*

Cite This: <https://doi.org/10.1021/jacs.3c03455>

Read Online

ACCESS |



Metrics &amp; More

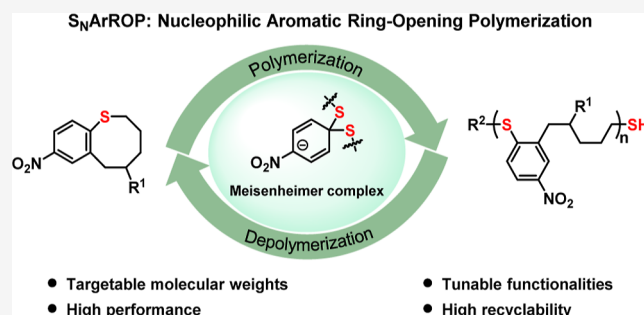


Article Recommendations



Supporting Information

**ABSTRACT:** The development of chemically recyclable polymers with desirable properties is a long-standing but challenging goal in polymer science. Central to this challenge is the need for reversible chemical reactions that can equilibrate at rapid rates and provide efficient polymerization and depolymerization cycles. Based on the dynamic chemistry of nucleophilic aromatic substitution ( $S_NAr$ ), we report a chemically recyclable polythioether system derived from readily accessible benzothioecane (BT) monomers. This system represents the first example of a well-defined monomer platform capable of chain-growth ring-opening polymerization through an  $S_NAr$  manifold. The polymerizations reach completion in minutes, and the pendant functionalities are easily customized to tune material properties or render the polymers amenable to further functionalization. The resulting polythioether materials exhibit comparable performance to commercial thermoplastics and can be depolymerized to the original monomers in high yields.



## INTRODUCTION

Synthetic polymers are widely used in daily life owing to their wide-ranging functionalities and properties. However, their mass production and consumption, coupled with high durability, result in enormous plastic waste at the end of their useful life.<sup>1–3</sup> This end-of-life issue of polymers not only has caused serious environmental and economic challenges but also makes them unsustainable if they cannot be recycled, as 90% of synthetic polymers are derived from finite fossil fuels.<sup>4</sup> Existing approaches to addressing the sustainability issue include mechanical recycling,<sup>5–7</sup> upcycling to value-added chemicals,<sup>8–12</sup> and chemical recycling to monomer (CRM),<sup>13–16</sup> among which CRM enables an attractive circular monomer life cycle and economy.

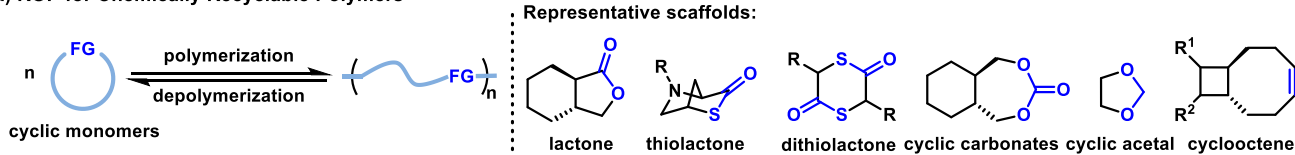
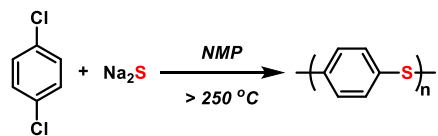
Several classes of designed polymers that are suitable for CRM, such as polyesters,<sup>17–20</sup> polythioesters,<sup>21–24</sup> polyacetals,<sup>25</sup> polycarbonates,<sup>26</sup> fused cyclooctene derivatives,<sup>27</sup> and others,<sup>28–32</sup> have been recently developed (Figure 1a). A common feature among all of these monomer classes is propagation through a ring-opening polymerization (ROP) mechanism and the presence of modest monomer ring strain that gives rise to a low ceiling temperature ( $T_c$ ). By subjecting these polymers to suitable triggers at elevated temperatures and/or reduced concentrations, the polymers can revert back to their constituent monomers through back-biting and cyclization reactions. Coupled to the overall thermodynamic challenge of identifying monomers with suitable  $T_c$  is the challenge of producing polymers with desirable material properties. Chen

and co-workers reported the ROP of trans-cyclohexyl-fused  $\gamma$ -butyrolactone, and the polymer exhibited good thermal stability (decomposition temperature  $T_d \sim 340$  °C) and high tensile strength ( $\sigma_B \sim 55$  MPa).<sup>18</sup> Through a reversible deactivation cationic ROP, Coates and co-workers synthesized poly(1,3-dioxolane), a thermally stable plastic with high tensile strength ( $\sigma_B \sim 40$  MPa).<sup>25</sup> Considering the relatively limited application potential of most CRM polymers reported to date, exploration of new concepts for ring-opening polymerization is targeted in this work.



To identify suitable chemistries for a new CRM platform, inspiration was found in the dynamic covalent chemistry of nucleophilic aromatic substitution ( $S_NAr$ ).<sup>33–38</sup> While numerous high-performance materials have been prepared and industrially used through  $S_NAr$  polymerization (Figure 1b), limited reports have taken advantage of the chemistry's inherent reversibility.<sup>39–41</sup> The pioneering work by Swager and Ong leveraged this feature to design error-correcting aryl sulfide network polymers (Figure 1c).<sup>42</sup> To merge this concept with the potential for recyclability to monomer, a cyclic aromatic thioether capable of  $S_NAr$  was envisioned that could be

Received: April 3, 2023




## a) ROP for Chemically Recyclable Polymers

b) Classical  $S_NAr$  Condensation for Polymer Synthesis


## c) Dynamic Self-Correcting Networks (Swager 2018)

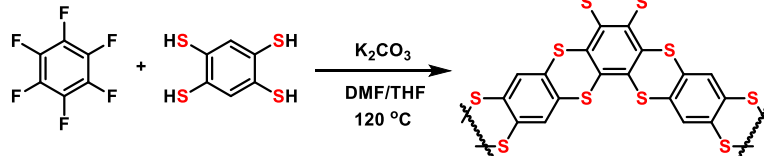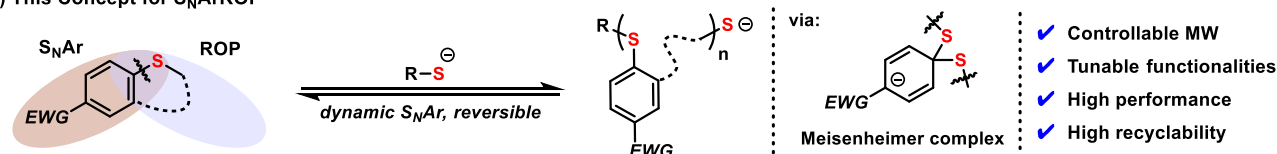d) This Concept for  $S_NAr$ ROP

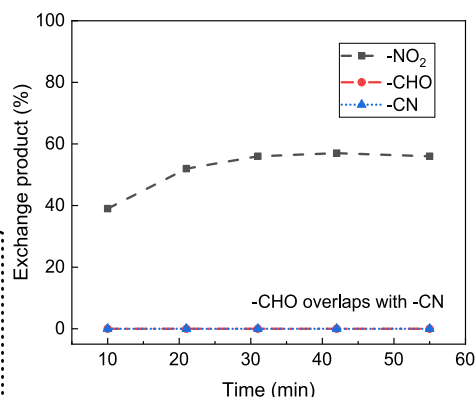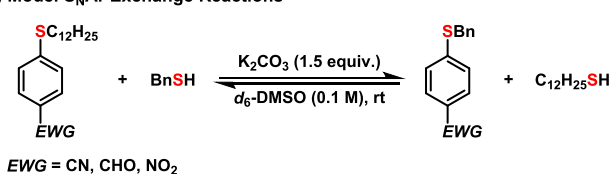
**Figure 1.** Designs of nucleophilic aromatic ring-opening polymerization ( $S_NAr$ ROP). (a) Established cyclic monomer scaffolds for preparing chemically recyclable polymers. (b) Classical  $S_NAr$  condensation for the preparation of poly(phenylene sulfide) (PPS). (c) Dynamic self-correcting  $S_NAr$  condensation for the synthesis of porous polymer networks. (d) New concept for  $S_NAr$ ROP for the synthesis of chemically recyclable polythioethers. The combination of dynamic  $S_NAr$  chemistry and an appropriate ring size for ROP enable the reversibility of this  $S_NAr$ ROP strategy.

a) Model  $S_NAr$  Exchange Reactionsb) Calculated  $\Delta H$  for  $S_NAr$ ROP with Different Ring Size from 5 to 8

**Figure 2.** Identifying the appropriate electron withdrawing group and ring size for the BT monomers. (a) Exchange reactions showing rapid equilibrium established with *p*-NO<sub>2</sub> substituted phenyl sulfide substrate at room temperature but no conversion from the -CN, and -CHO substrates. (b) Calculated  $\Delta H$  for  $S_NAr$ ROP with different ring sizes from 5 to 8, suggesting enthalpically favorable polymerization of 7- and 8-membered ring substrates.

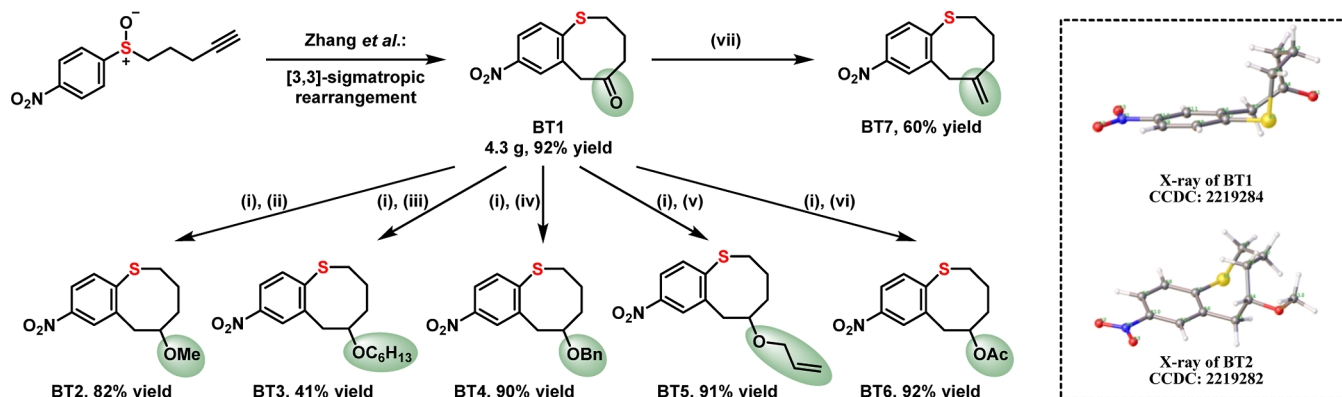

**Figure 3.** Synthesis and characterization of the BT monomers. Synthesis of the 8-membered ring substrate BT1 through an efficient [3,3]-sigmatropic rearrangement and its convenient transformation to BT2-BT7. (i) NaBH<sub>4</sub>, MeOH, 0 °C. (ii) NaH, MeI, THF. (iii) NaH, C<sub>6</sub>H<sub>13</sub>I, THF. (iv) NaH, BnBr, DMF. (v) NaH, allyl bromide, DMF. (vi) Ac<sub>2</sub>O, DMAP, pyridine. (vii) <sup>t</sup>BuOK, PPh<sub>3</sub>PMeBr, THF. The X-ray of BT1 and BT2 are shown as the insert.

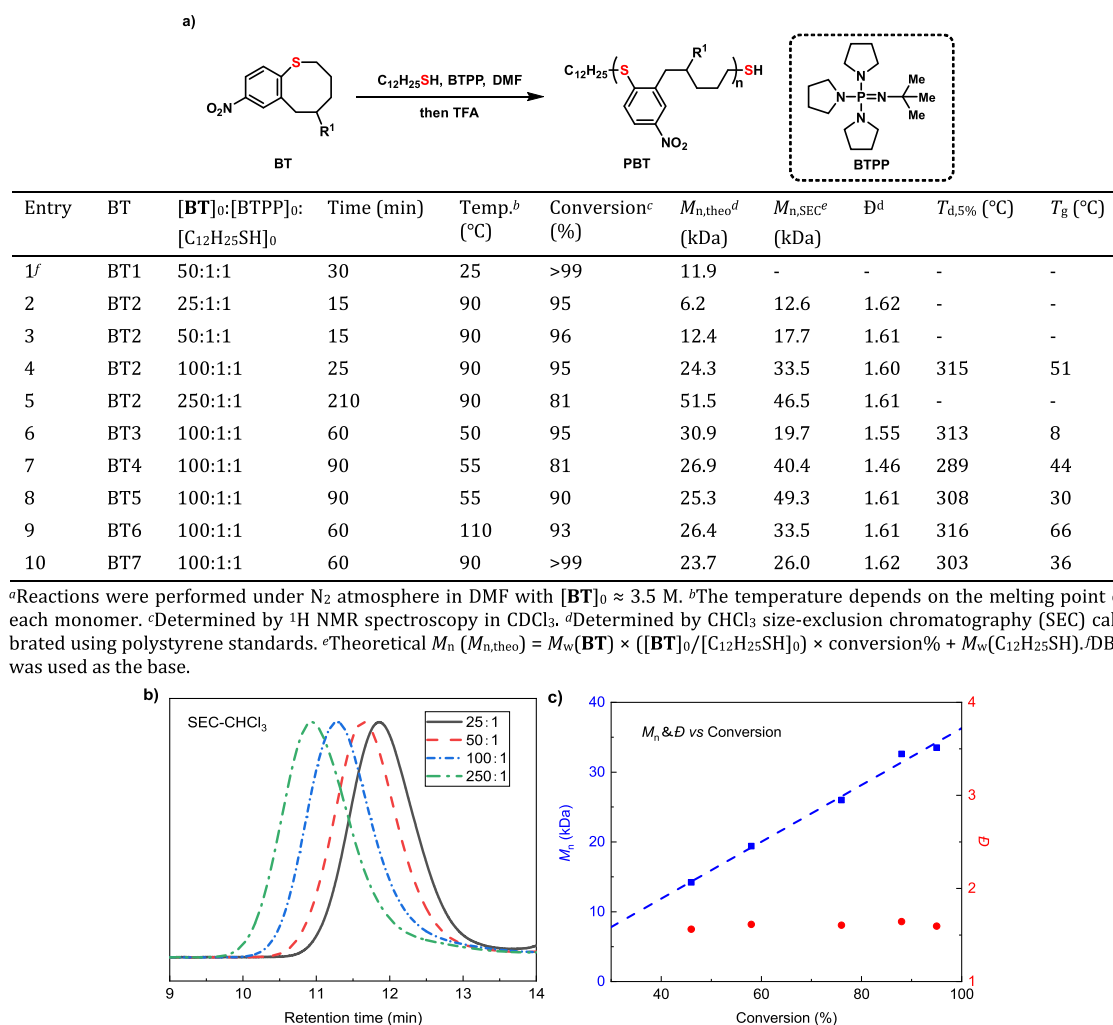

**Figure 4.** S<sub>N</sub>ArROP of BT monomers and characterization of PBTs. (a) Results of BT polymerizations by BTTP-based catalytic systems. (b) SEC curves for PBT2 produced at different [BT2]<sub>0</sub>/[BTTP]<sub>0</sub>/[C<sub>12</sub>H<sub>25</sub>SH]<sub>0</sub> ratios. (c) M<sub>n</sub>–conversion correlation (blue) and Đ–conversion correlation (red) of S<sub>N</sub>ArROP of BT2.


polymerized through nucleophilic aromatic ring-opening polymerization (S<sub>N</sub>ArROP) (Figure 1d). While some macrocyclic systems have been shown to polymerize, a well-defined monomer for chain-growth ring-opening polymerization through S<sub>N</sub>Ar chemistry has yet to be realized.<sup>43</sup>

## RESULTS AND DISCUSSION

**Monomer Design and Synthesis.** To identify the feasibility of a ring-opening monomer for S<sub>N</sub>Ar, exchange reactions were examined between benzyl mercaptan (BnSH) and aryl dodecyl sulfides with different electron-withdrawing para-substituents (CN, CHO, and NO<sub>2</sub>). While *p*-CN and *p*-CHO-substituted substrates provide no conversion at room temperature and low conversion at 60 °C, *p*-NO<sub>2</sub>-phenyl dodecyl sulfide reacted with BnSH smoothly and reached equilibrium in approximately 30 min at room temperature (Figure 2a and Supplementary Figures S7–S9). Based on our recently developed first-principles computational methodology, the ring-opening polymerization (ROP) enthalpy (Δ*H*) for NO<sub>2</sub>-substituted cyclic monomer scaffolds was calculated (Figure 2b).<sup>44</sup> The results showed that the 7- and 8-membered cyclic aryl thioethers have sufficient Δ*H* values to promote polymerization (−16.43 and −27.97 kJ/mol, respectively), whereas the 5- and 6-membered substrates were predicted to be

insufficiently strained (0.26 and −1.08 kJ/mol). Fortunately, the [3,3]-sigmatropic rearrangement of alkynyl sulfoxides reported by Zhang and co-workers offered expedient and scalable access to 8-membered ring aryl sulfides (BT1) bearing the requisite nitro-group substitution (Figure 3).<sup>45</sup> Additionally, the parent ketone (BT1) was readily reduced to an alcohol that could be further derivatized with a variety of electrophiles to install side-chain functionalities (BT2–BT6) or transformed to BT7 containing an exocyclic C=C double bond through the Wittig reaction (Figure 3). In addition to full characterization of all monomers through <sup>1</sup>H NMR, <sup>13</sup>C NMR, and mass spectrometry, X-ray structures of BT1 and BT2 were also obtained (Figure 3). The X-ray studies showed that BT1 and BT2 exist in the crystal state exclusively in the boat-chair conformation, and there were two rotamers in BT1 with populations of 97.7 and 2.3%, respectively.

**Polymerization Studies.** At the outset, the polymerizability of BT1 was probed via measuring its exchange reaction with BnSH, and a rapid exchange reaction was finished between BT1 and BnSH in DMSO-*d*<sub>6</sub> with K<sub>2</sub>CO<sub>3</sub> as the base at room temperature (Supplementary Figure S10). To keep the polymerization homogeneous, the organic base DBU instead of the inorganic base K<sub>2</sub>CO<sub>3</sub> was used. A preliminary polymerization test with a [BT1]<sub>0</sub>/[DBU]<sub>0</sub>/[C<sub>12</sub>H<sub>25</sub>SH]<sub>0</sub>

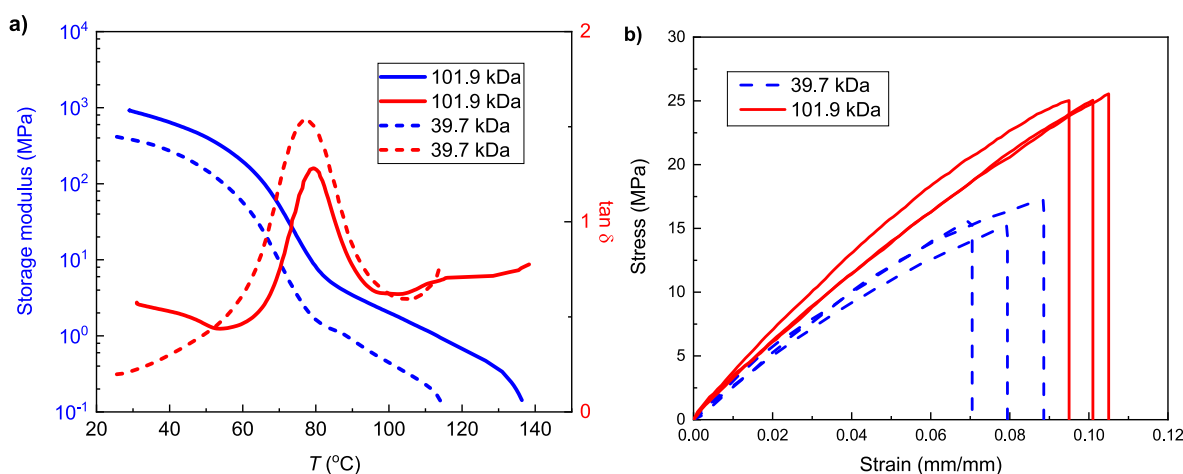

**Figure 5.** Mechanical properties of PBT2. (a) DMA storage modulus and  $\tan \delta$  profiles of PBT2 with different molecular weights. (b) Tensile stress–strain curves of PBT2 with different molecular weights.

ratio of 50:1:1 yielded a poorly soluble polymer **PBT1** with almost full conversion (Figure 4a, entry 1). The methyl ether side-chain of **BT2** improved the solubility of the corresponding polymer and facilitated the study of the molecular weight and dispersity through gel permeation chromatography (GPC) while still maintaining high conversions. Solvent choice proved to be critical for polymerization. Fast reaction rates and high conversions were generally found in polar aprotic solvents, including dimethyl sulfoxide (DMSO), dimethylformamide (DMF), dimethylacetamide (DMA), *N*-methyl-2-pyrrolidone (NMP), and *N,N'*-dimethylpropyleneurea (DMPU), while no reaction at all in relatively less polar solvents such as chloroform ( $\text{CHCl}_3$ ), 1,2-dichloroethane (DCE), and tetrahydrofuran (THF) (Supplementary Table S1). These results can be explained by the requirement of a polar environment to stabilize the Meisenheimer intermediate (Figure 1d) in the nucleophilic aromatic substitution step.<sup>46–48</sup> While the experimental  $M_n$  values were slightly higher than those calculated from the ratio of  $[\text{M}]_0/[\text{I}]_0$  and conversion, targetable molecular weights were readily obtained. A small peak in the lower molecular weight range was observed in the GPC traces, suggesting the possible formation of cyclic oligomer byproducts, which was further confirmed by matrix-assisted laser desorption/ionization-time-of-flight (MALDI-TOF) mass spectrometry (Supplementary Figures S12 and S13). By increasing the monomer concentration, the cyclic oligomer byproducts were limited, and a unimodal high-molecular-weight polymers were obtained (Supplementary Table S2). Interestingly, the polymerization was found to readily proceed to high conversion at a wide range of temperatures (90 to 140 °C) (Supplementary Table S2). A variety of bases and thiol initiators were further screened, and strong bases with higher  $pK_a$  and more nucleophilic thiolates were found beneficial for the polymerization (Supplementary Tables S4 and S5).


Under the optimized reaction conditions, a series of molecular weight targets were obtained by adjusting the monomer-to-initiator ratio ( $[\text{BT2}]_0/[\text{BTPP}]_0/[\text{C}_{12}\text{H}_{25}\text{SH}]_0$ ) from 25:1:1 to 250:1:1 (Figure 4a, entries 2–5). Moreover, the molecular weight increased linearly as the monomer to initiator ratio increased, while the corresponding dispersity ( $\bar{D}$ ) remained at a modest value ( $\sim 1.60$ ) during polymerization (Figure 4b). These data strongly support a chain-growth mechanism to the polymerization with chain-transfer events occurring between

propagating polymers and the aryl sulfide backbone. Next, the generality of the  $\text{S}_\text{N}\text{Ar}$ ROP strategy was investigated using monomers bearing different substituents ( $\text{O}-\text{C}_6\text{H}_{13}$ ,  $\text{O}-\text{Bn}$ ,  $\text{O}-\text{allyl}$ ,  $\text{O}-\text{Ac}$ , and  $\text{C}=\text{C}$ ). The  $\text{S}_\text{N}\text{Ar}$ ROP of these monomers was achieved at a temperature slightly higher than their melting points at a 3.5 M monomer concentration to ensure solubility throughout the polymerization (Figure 4a, entries 6–10). The corresponding polymers with molecular weight ranging from 19.7 to 49.3 kDa and consistent  $\bar{D}$  values ranging from 1.46 to 1.62 were obtained from a  $[\text{BT}]_0/[\text{BTPP}]_0/[\text{C}_{12}\text{H}_{25}\text{SH}]_0$  ratio of 100:1:1. The substituents showed a slight influence on the polymerization reactivity, as shown by the conversion ranging from 81 to 99%. The convenient introduction of these various functional groups enables the tuning of the resulting material's properties as shown below.

**Thermal and Mechanical Properties.** Thermogravimetric analysis (TGA) and differential scanning calorimetry (DSC) were used to measure the thermal properties for each poly(aryl thioether). All the produced polymers obtained with  $[\text{BT}]_0/[\text{BTPP}]_0/[\text{C}_{12}\text{H}_{25}\text{SH}]_0 = 100:1:1$  displayed high thermal stability with a range of thermal decomposition temperature  $T_d$  (defined as the temperature causing a 5% weight loss) from 289 to 316 °C (Figure 4a and Supplementary Figure S16). Depending on the pendant groups on the monomers, a wide range of  $T_g$ s from 8 to 66 °C can be accessed (Figure 4a and Supplementary Figure S16). The absence of clear melting transitions indicates the amorphous character of these polymers, which could be explained by atactic microstructures generated from the racemic monomers.

Further investigation was focused on the thermal and mechanical properties of these PBT samples, especially the effect of the molecular weight on these properties. PBT2 with two different  $M_n$  (39.7 kDa and 101.9 kDa) was prepared. PBT2s exhibited the typical behavior of a thermoplastic polymer as shown by dynamic mechanical analysis (DMA) (Figure 5). Both samples possessed relatively high storage modulus ( $E'$ ) at room temperature as glassy polymers. However, after the glass transition region with  $T_g$  values around 80 °C (as defined by the peak maxima of  $\tan \delta$ ),  $E'$  continually decreased until a quick drop to the viscous flow state due to melting (Figure 5a). The sample with a higher molecular weight displayed both higher  $E'$  and  $T_g$  as expected ( $M_n = 39.7$  kDa:  $E' = 375.1$  MPa (30 °C),  $T_g = 77.8$  °C;  $M_n = 101.9$  kDa:  $E' = 1243.8$  MPa (30 °C),  $T_g = 79.5$



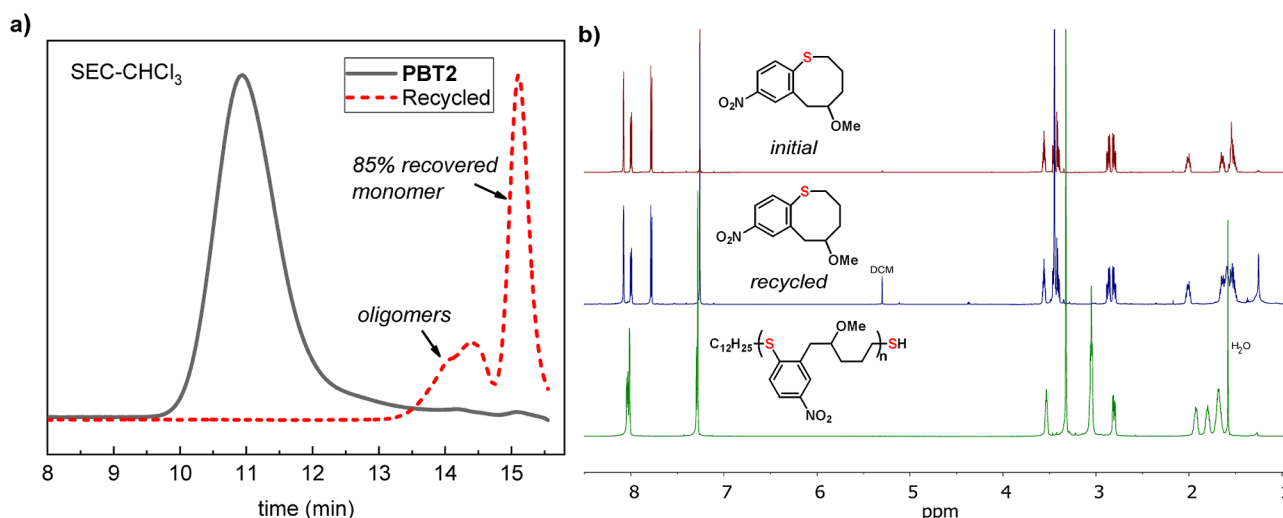

**Figure 6.** Chemical recyclability of PBT2. (a) SEC curves for depolymerization of PBT2 (46.5 kDa) with substoichiometric DBU and  $C_{12}H_{25}SH$  (0.55 equiv relative to repeat units). (b) Overlays of  $^1H$  NMR spectra of initial and recycled BT2 and PBT2.

$^{\circ}C$ ). Furthermore, tensile testing of the PBT2 showed the same trend as a glassy polymer with Young's modulus  $E = 275.6 \pm 19.9$  and  $349.9 \pm 18.76$  MPa, ultimate tensile strength  $\sigma = 16.07 \pm 0.84$  and  $25.21 \pm 0.24$  MPa, and elongation at break  $\epsilon = 7.95 \pm 0.74$  and  $10.03 \pm 0.41\%$  for the 39.7 and 101.9 kDa samples, respectively (Figure S5b). The tensile performance is within the range of some commonly used thermoplastics such as polyethylene (PE), ethylene vinyl acetate (EVA), and polyvinyl chloride (PVC), suggesting applications potential upon further increases to molecular weight or the addition of plasticizers.

**Chemical Recyclability.** As an effort to achieve the original purpose of designing recyclable polymers with robust and durable behavior, the advantages of PBTs in mechanical properties led us to explore the recyclability to monomers of these polymers. The initial attempts to depolymerize the parent polymer PBT2 from the chain end by adding the DBU were unsuccessful, but the introduction of additional thiol was found to help conversion through cleaving segments from the polymer backbone for depropagation (Supplementary Figure S19 and Figure S20). By adding 0.55 equivalent of DBU and  $C_{12}H_{25}SH$  relative to the repeat unit at a temperature of  $90^{\circ}C$  and a concentration of 10 mg/mL, an isolated yield of 85% for BT2 was achieved (Figure 6). This depolymerization is likely initiated through backbone cleavage due to reversible  $S_NAr$  chemistry, which is further supported by the successful depolymerization of an end-capped PBT5 (capped with iodoacetamide) producing monomer BT5 in 70% yield (Supplementary Figure S21).

## CONCLUSIONS

In conclusion, the dynamic reversibility of  $S_NAr$  chemistry and ring-opening polymerization have been successfully merged into a well-defined monomer platform for the first time.  $S_NArROP$  of BTs is an effective and powerful strategy for the synthesis of chemically recyclable polythioethers. The facile modification of the monomer scaffold leads to readily tunable material properties, and the high recyclability suggests that the BT platform is a robust candidate for the design of new dynamic and depolymerizable polymers capable of CRM. Further studies on post-polymerization modification to chemically crosslink and 3D print recyclable materials are currently underway.

## ASSOCIATED CONTENT

### Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/jacs.3c03455>.

Experimental procedure and spectroscopic data for all new compounds and X-ray crystallographic data for BT1 and BT2 (PDF).

### Accession Codes

CCDC 2219282 and 2219284 contain the supplementary crystallographic data for this paper. These data can be obtained free of charge via [www.ccdc.cam.ac.uk/data\\_request/cif](http://www.ccdc.cam.ac.uk/data_request/cif), or by emailing [data\\_request@ccdc.cam.ac.uk](mailto:data_request@ccdc.cam.ac.uk), or by contacting The Cambridge Crystallographic Data Centre, 12 Union Road, Cambridge CB2 1EZ, UK; fax: +44 1223 336033.

## AUTHOR INFORMATION

### Corresponding Author

Will R. Gutekunst — School of Chemistry and Biochemistry, Georgia Institute of Technology, Atlanta, Georgia 30332, United States; [orcid.org/0000-0002-2427-4431](https://orcid.org/0000-0002-2427-4431); Email: [willgute@gatech.edu](mailto:willgute@gatech.edu)

### Authors

Yong-Liang Su — School of Chemistry and Biochemistry, Georgia Institute of Technology, Atlanta, Georgia 30332, United States  
 Liang Yue — School of Mechanical Engineering, Georgia Institute of Technology, Atlanta, Georgia 30332, United States  
 Huan Tran — School of Materials Science and Engineering, Georgia Institute of Technology, Atlanta, Georgia 30332, United States; [orcid.org/0000-0002-8093-9426](https://orcid.org/0000-0002-8093-9426)  
 Mizhi Xu — School of Chemistry and Biochemistry, Georgia Institute of Technology, Atlanta, Georgia 30332, United States; [orcid.org/0000-0003-4595-0109](https://orcid.org/0000-0003-4595-0109)  
 Anthony Engler — School of Chemical and Biomolecular Engineering, Georgia Institute of Technology, Atlanta, Georgia 30332, United States  
 Rampi Ramprasad — School of Materials Science and Engineering, Georgia Institute of Technology, Atlanta, Georgia 30332, United States; [orcid.org/0000-0003-4630-1565](https://orcid.org/0000-0003-4630-1565)

H. Jerry Qi – School of Mechanical Engineering, Georgia Institute of Technology, Atlanta, Georgia 30332, United States; [orcid.org/0000-0002-3212-5284](https://orcid.org/0000-0002-3212-5284)

Complete contact information is available at:  
<https://pubs.acs.org/10.1021/jacs.3c03455>

## Notes

The authors declare no competing financial interest.

## ACKNOWLEDGMENTS

This work was supported by ONR MURI N00014-20-1-2586. We acknowledge support from the Organic Materials Characterization Laboratory (OMCL) at GT for use of the shared characterization facility. We thank Dr. John Bacsa (Emory University) for assistance with X-ray crystallography.

## REFERENCES

- (1) Stubbins, A.; Law, K. L.; Muñoz, S. E.; Bianchi, T. S.; Zhu, L. Plastics in the Earth System. *Science* **2021**, *373*, 51–55.
- (2) MacLeod, M.; Arp, H. P. H.; Tekman, M. B.; Jahnke, A. The Global Threat from Plastic Pollution. *Science* **2021**, *373*, 61–65.
- (3) Geyer, R.; Jambeck, J. R.; Law, K. L. Production, Use, and Fate of All Plastics Ever Made. *Sci. Adv.* **2017**, *3*, 25–29.
- (4) *The New Plastics Economy: Rethinking the Future of Plastics and Catalysing Action* Ellen MacArthur Foundation, 2017.
- (5) Schyns, Z. O. G.; Shaver, M. P. Mechanical recycling of packaging plastics: A review. *Macromol. Rapid Commun.* **2021**, *42*, No. e2000415.
- (6) Billiet, S.; Trenor, S. R. 100th Anniversary of Macromolecular Science Viewpoint: Needs for Plastics Packaging Circularity. *ACS Macro Lett.* **2020**, *9*, 1376–1390.
- (7) Vollmer, I.; Jenks, M. J. F.; Roelands, M. C. P.; White, R. J.; Harmelen, T.; Wild, P.; Laan, G. P.; Meirer, F.; Keurentjes, J. T. F.; Weckhuysen, B. M. Beyond Mechanical Recycling: Giving New Life to Plastic Waste. *Angew. Chem., Int. Ed.* **2020**, *59*, 15402–15423.
- (8) Rahimi, A.; García, J. M. Chemical Recycling of waste plastics for new materials production. *Nat. Rev. Chem.* **2017**, *1*, 0046.
- (9) Jehanno, C.; Perez-Madrigal, M. M.; Demarteau, J.; Sardon, H.; Dove, A. P. Organocatalysis for Depolymerisation. *Polym. Chem.* **2019**, *10*, 172–186.
- (10) Zhang, F.; Zeng, M.; Yappert, R. D.; Sun, J.; Lee, Y. H.; LaPointe, A. M.; Peters, B.; Abu-Omar, M. M.; Scott, S. L. Polyethylene upcycling to long-chain alkylaromatics by tandem hydrogenolysis/aromatization. *Science* **2020**, *370*, 437–441.
- (11) Korley, L. T. J.; Epps, T. H.; Helms, B. A.; Ryan, A. J. Toward polymer upcycling-adding value and tackling circularity. *Science* **2021**, *373*, 66–69.
- (12) Ellis, L. D.; Rorrer, N. A.; Sullivan, K. P.; Otto, M.; McGeehan, J. E.; Román-Leshkov, Y.; Wierckx, N.; Beckham, G. T. Chemical and biological catalysis for plastics recycling and upcycling. *Nat. Catal.* **2021**, *4*, 539–556.
- (13) Hong, M.; Chen, E. Y. X. Chemically Recyclable Polymers: A Circular Economy Approach to Sustainability. *Green Chem.* **2017**, *19*, 3692–3706.
- (14) Schneiderman, D. K.; Hillmyer, M. A. 50th Anniversary Perspective: There Is a Great Future in Sustainable Polymers. *Macromolecules* **2017**, *50*, 3733–3749.
- (15) Lu, X.-B.; Liu, Y.; Zhou, H. Learning Nature: Recyclable Monomers and Polymers. *Chem.–Eur. J.* **2018**, *24*, 11255–11266.
- (16) Coates, G. W.; Getzler, Y. D. Y. L. Chemical Recycling to Monomer for an Ideal, Circular Polymer Economy. *Nat. Rev. Mater.* **2020**, *5*, 501–516.
- (17) Schneiderman, D. K.; Vanderlaan, M. E.; Mannion, A. M.; Panthani, T. R.; Batiste, D. C.; Wang, J. Z.; Bates, F. S.; Macosko, C. W.; Hillmyer, M. A. Chemically Recyclable Biobased Polyurethanes. *ACS Macro Lett.* **2016**, *5*, 515–518.
- (18) Zhu, J.-B.; Watson, E. M.; Tang, J.; Chen, E. Y.-X. A Synthetic Polymer System with Repeatable Chemical Recyclability. *Science* **2018**, *360*, 398–403.
- (19) Tang, X.; Chen, E. Y. X. Toward Infinitely Recyclable Plastics Derived from Renewable Cyclic Esters. *Chem* **2019**, *5*, 284–312.
- (20) Häußler, M.; Eck, M.; Rothauer, D.; Mecking, S. Closed-Loop Recycling of Polyethylene-like Materials. *Nature* **2021**, *590*, 423–427.
- (21) Yuan, J.; Xiong, W.; Zhou, X.; Zhang, Y.; Shi, D.; Li, Z.; Lu, H. 4-Hydroxyproline-Derived Sustainable Polythioesters: Controlled Ring-Opening Polymerization, Complete Recyclability, and Facile Functionalization. *J. Am. Chem. Soc.* **2019**, *141*, 4928–4935.
- (22) Wang, Y.; Li, M.; Chen, J.; Tao, Y.; Wang, X. O-to-S Substitution Enables Dovetailing Conflicting Cyclizability, Polymerizability, and Recyclability: Dithiolactone vs. Dilactone. *Angew. Chem., Int. Ed.* **2021**, *60*, 22547–22553.
- (23) Stellmach, K. A.; Paul, M. K.; Xu, M.; Su, Y.-L.; Fu, L.; Toland, A. R.; Tran, H.; Chen, L.; Ramprasad, R.; Gutekunst, W. R. Modulating Polymerization Thermodynamics of Thiolactones Through Substituent and Heteroatom Incorporation. *ACS Macro Lett.* **2022**, *11*, 895–901.
- (24) Wang, Y.; Zhu, Y.; Lv, W.; Wang, X.; Tao, Y. Tough while Recyclable Plastics Enabled by Monothiodilactone Monomers. *J. Am. Chem. Soc.* **2023**, *145*, 1877–1885.
- (25) Abel, B. A.; Snyder, R. L.; Coates, G. W. Chemically Recyclable Thermoplastics from Reversible-Deactivation Polymerization of Cyclic Acetals. *Science* **2021**, *373*, 783–789.
- (26) Zhang, W.; Dai, J.; Wu, Y.-C.; Chen, J.-X.; Shan, S.-Y.; Cai, Z.; Zhu, J.-B. Highly Reactive Cyclic Carbonates with a Fused Ring toward Functionalizable and Recyclable Polycarbonates. *ACS Macro Lett.* **2022**, *11*, 173–178.
- (27) Sathe, D.; Zhou, J.; Chen, H.; Su, H.-W.; Xie, W.; Hsu, T.-G.; Schrage, B. R.; Smith, T.; Ziegler, C. J.; Wang, J. Olefin Metathesis-Based Chemically Recyclable Polymers Enabled by Fused-Ring Monomers. *Nat. Chem.* **2021**, *13*, 743–750.
- (28) Liu, Y.; Jia, Y.; Wu, Q.; Moore, J. S. Architecture-Controlled Ring-Opening Polymerization for Dynamic Covalent Poly(Disulfide)S. *J. Am. Chem. Soc.* **2019**, *141*, 17075–17080.
- (29) Christensen, P. R.; Scheuermann, A. M.; Loeffler, K. E.; Helms, B. A. Closed-Loop Recycling of Plastics Enabled by Dynamic Covalent Diketoneamine Bonds. *Nat. Chem.* **2019**, *11*, 442–448.
- (30) Wang, H.; Giardino, G. J.; Chen, R.; Yang, C.; Niu, J.; Wang, D. Photocatalytic Depolymerization of Native Lignin toward Chemically Recyclable Polymer Networks. *ACS Cent. Sci.* **2023**, *9*, 48–55.
- (31) Wang, Y. C.; Li, M. S.; Wang, S. X.; Tao, Y. H.; Wang, X. H. S. -Carboxyanhydrides: Ultrafast and Selective Ring-Opening Polymerizations Towards Well-defined Functionalized Polythioesters. *Angew. Chem., Int. Ed.* **2021**, *60*, 10798–10805.
- (32) Luo, X.; Wei, Z.; Seo, B.; Hu, Q.; Wang, X.; Romo, J. A.; Jain, M.; Cakmak, M.; Boudouris, B. W.; Zhao, K.; Mei, J.; Savoie, B. M.; Dou, L. Circularly Recyclable Polymers Featuring Topochemically Weakened Carbon-Carbon Bonds. *J. Am. Chem. Soc.* **2022**, *144*, 16588–16597.
- (33) Rowan, S. J.; Cantrill, S. J.; Cousins, G. R. L.; Sanders, J. K. M.; Stoddart, J. F. Dynamic covalent chemistry. *Angew. Chem., Int. Ed.* **2002**, *41*, 898–952.
- (34) Zhang, W.; Jin, Y. *Dynamic Covalent Chemistry: Principles, Reactions, and Applications*; John Wiley & Sons, 2017.
- (35) Jin, Y.; Wang, Q.; Taynton, P.; Zhang, W. Dynamic covalent chemistry approaches toward macrocycles, molecular cages, and polymers. *Acc. Chem. Res.* **2014**, *47*, 1575–1586.
- (36) Zou, W.; Dong, J.; Luo, Y.; Zhao, Q.; Xie, T. Dynamic covalent polymer networks: from old chemistry to modern day innovations. *Adv. Mater.* **2017**, *29*, 1606100.
- (37) Orrillo, A. G.; Furlan, R. L. E. Sulfur in Dynamic Covalent Chemistry. *Angew. Chem., Int. Ed.* **2022**, No. e202201168.
- (38) Lei, Z.; Chen, H.; Luo, C.; Rong, Y.; Hu, Y.; Jin, Y.; Long, R.; Yu, K.; Zhang, W. Recyclable and malleable thermosets enabled by activating dormant dynamic linkages. *Nat. Chem.* **2022**, *14*, 1399–1404.

- (39) Robb, M. J.; Knauss, D. M. Poly(Arylene Sulfide)s by Nucleophilic Aromatic Substitution Polymerization of 2,7-Difluorothianthrene. *J. Polym. Sci., Part A: Polym. Chem.* **2009**, *47*, 2453–2461.
- (40) Mullins, M. J.; Woo, E. P.; Balon, K. E.; Murray, D. J.; Chen, C. C. U.S. Patent 5 264 538, 1993.
- (41) Jiang, H.; Chen, T.; Qi, Y.; Xu, J. Macrocyclic Oligomeric Arylene Ether Ketones: Synthesis and Polymerization. *Polym. J.* **1998**, *30*, 300–303.
- (42) Ong, W. J.; Swager, T. M. Dynamic self-correcting nucleophilic aromatic substitution. *Nat. Chem.* **2018**, *10*, 1023–1030.
- (43) Stagnaro, P.; Brunengo, E.; Conzatti, L. ED-ROP of macrocyclic oligomers: A synthetic tool for multicomponent polymer materials. *ARKIVOC* **2021**, *2021*, 174–221.
- (44) Tran, H.; Toland, A.; Stellmach, K.; Paul, M. K.; Gutekunst, W.; Ramprasad, R. Toward Recyclable Polymers: Ring-Opening Polymerization Enthalpy from First-Principles. *J. Phys. Chem. Lett.* **2022**, *13*, 4778–4785.
- (45) Lu, B.; Li, Y.; Wang, Y.; Aue, D. H.; Luo, Y.; Zhang, L. [3,3]-Sigmatropic Rearrangement versus Carbene Formation in Gold-Catalyzed Transformations of Alkynyl Aryl Sulfoxides: Mechanistic Studies and Expanded Reaction Scope. *J. Am. Chem. Soc.* **2013**, *135*, 8512–8524.
- (46) Terrier, F. *Modern Nucleophilic Aromatic Substitutions*; Wiley-VCH: Weinheim, 2013.
- (47) Kwan, E. E.; Zeng, Y.; Besser, H. A.; Jacobsen, E. N. Concerted Nucleophilic Aromatic Substitutions. *Nat. Chem.* **2018**, *10*, 917–923.
- (48) Rohrbach, S.; Murphy, J. A.; Tuttle, T. Computational Study on the Boundary Between the Concerted and Stepwise Mechanism of Bimolecular  $S_NAr$  Reactions. *J. Am. Chem. Soc.* **2020**, *142*, 14871–14876.